



Universidad  
Carlos III de Madrid



This is a postprint version of the following published document:

Baselga, J., Piérola, I. F., Hernández-Fuentes, I. & Llorente, M. A. (1988). Stress-strain behavior of polyacrylamide networks. *Makromolekulare Chemie. Macromolecular Symposia*, 20-21 (1), pp. 369–382.

DOI: [10.1002/masy.19880200139](https://doi.org/10.1002/masy.19880200139)

© Wiley, 1988

# STRESS-STRAIN BEHAVIOR OF POLYACRYLAMIDE NETWORKS

J. Baselga<sup>1</sup>; I.F. Pierola<sup>1</sup>; I. Hernandez-Fuentes<sup>1</sup> and M.A. Llorente<sup>\*2</sup>

<sup>1</sup>. Departamento de Química Física. Facultad de CC. Químicas. Universidad Complutense de Madrid. 28040 Madrid, SPAIN.

<sup>2</sup>. Departamento de Química Física. Facultad de CC. Universidad Nacional de Educación a Distancia (UNED) 28040 Madrid, SPAIN.

## ABSTRACT

The mechanical properties of a number of polyacryl-amide gels have been studied by means of elastic measurements in elongation. Different gels were prepared by varying the proportions of both comonomers, acrylamide and N,N'-methylene-bisacrylamide which is used as crosslinker, and a very broad range of concentrations was covered. The most important results considered were the elastic phantom modulus, the degree of (equilibrium) swelling and the elongation at rupture. The data were interpreted in terms of the mechanism of the gelation process taking into account a number of parameters that affect the final structure of the gels: comonomer reactivities, sequence length distributions and cycles formation. Consideration of these factors can explain properly all the features of the elastic results as well as some other properties related to the gelation process such as gel point data.

## INTRODUCTION

Polyacrylamide (PAA) gels have numerous practical applications and are broadly used in many research techniques (electrophoresis, chromatography, etc.) These gels are usually obtained by radical copolymerization of acrylamide (AA) and a divinyl comonomer, typically N,N'-methylenebisacrylamide (BA) as crosslinker. The resulting gel structure is very much dependent

on the polymerization conditions, mainly on the total comonomer concentration ( $C_T$ ), and on the proportion of crosslinker (C). Results from techniques sensitive to very different properties<sup>1-8</sup> have shown that PAA gels are very heterogeneous, having a structure in which regions of very different degrees of crosslinking coexist. Several qualitative arguments based on the mechanism of the crosslinking reaction have been proposed<sup>2,3,5-7</sup> in order to interpret the properties of the system, but a more elaborated explanation is needed.

In previous studies performed on the kinetics of the gelation process we have found that a number of factors that would affect the final gel structure should be taken into account. In the first place BA, as a monomer, is more reactive than AA since it has two vinyl groups<sup>9,10</sup>. This is a common feature of other systems synthesized by vinyl-divinyl radical copolymerizations. As a result, BA units are not randomly distributed along the primary chains but they can form sequences involving several units<sup>10</sup>. On the other hand, under certain conditions, a large proportion of intramolecular cycles can be formed. This factor has been found to be of paramount importance to interpret the data on the degree of conversion at the gel point<sup>11</sup>.

In this work we have studied the mechanical properties of a number of PAA gels covering a wide range of total comonomer concentrations ( $C_T$ ) and proportion of crosslinker (C). The experiments have been mainly focussed on highly crosslinked gels for which previous studies are scarce. The results have been interpreted in terms of the above mentioned kinetic factors that are responsible for the final gel structure. A comprehensive explanation, which involves mechanical and ultimate properties, swelling equilibrium results and gel point data can be given.

## EXPERIMENTAL SECTION

Acrylamide (AA) and N,N'-methylenebisacrylamide (BA) were purchased from Eastman Kodak. BA was used after recrystallization from acetone. The redox pair potassium persulphate (PSK)/triethanolamine (TEA), both products from Carlo Erba, was used

as the room temperature initiator system. Water was purified from salts and organic matter by a Milli-Q equipment (Millipore) and filtered with a 0.45  $\mu\text{m}$  filter.

Details for the experimental method have been previously reported<sup>12</sup>. Elastic modulus of polyacrylamide (PAA) gels were determined from stress-strain measurements (in extension) on gel samples, immersed in pure water at swelling equilibrium at 30°C. The samples, with their final geometry, were prepared in a teflon-glass mould in which two pieces of a woven material were placed at both ends, thus resulting in a sample with firm extremities, suitable for mechanical measurements.

Two series of gels were synthesized, both with initiator concentrations:  $[\text{TEA}] = 8.51 \times 10^{-3} \text{M}$  and  $[\text{PSK}] = 6.57 \times 10^{-3} \text{M}$ . In the first one, the total comonomers concentration,  $C_T$ , was kept constant ( $C_T = 6.72 \text{ g/100ml}$ ) varying the percentage of cross-linking comonomer,  $C$  ( $0.663 < C < 14.5\% \text{ w/w}$ ). On the other hand, a second set of networks were studied in which  $C = 10\% \text{ w/w}$  and  $C_T$  ranged from 4.99 to 18.0 g/100ml.

The initial dimensions of the samples ( $L_0$  and cross-sectional area) were measured in a relaxed state of the samples, horizontally, to avoid the deformation self induced by the weight of the gels. Cross-sectional areas of the swollen samples were approximately 70  $\text{mm}^2$ .

The relaxation delay between successive experimental points depends not only on the relaxation of the sample, but on the new swelling equilibrium that must be attained, which is a function of the crosslinking density, and was found to be between 2 and 6 hours.

## RESULTS AND DISCUSSION

The elastic results have been interpreted by means of the modulus or "reduced force", which is defined by<sup>13</sup>

$$[f^*] = (f/A^*)v_{2s}^{1/3} / [\alpha - \alpha^{-2}] \quad (1)$$

where  $f$  is the elastic force at equilibrium;  $A^*$  is the cross-sectional area of the unstretched unswollen sample and  $v_{2s}$  is the degree of swelling of the sample (gel volume fraction) at the given deformation  $\alpha$  ( $\alpha = L/L_0$ ,  $L$  and  $L_0$  being the lengths

of the deformed and undeformed states respectively). As an approximation, the degree of swelling for each elongation has been expressed by<sup>14</sup>

$$v_{2s} = v_{2s}^{\circ} \cdot \alpha^{-3/5} \quad (2)$$

where  $v_{2s}^{\circ}$  is the volume fraction at swelling equilibrium in the undeformed state. The cross-sectional area of the dried gel  $A^*$ , has been obtained from the one of the swollen sample  $A_0$ , assuming isotropic swelling, by means of

$$A^* = A_0 (v_{2s}^{\circ})^{2/3} \quad (3)$$

Data were treated according to the Flory-Erman theory of rubber elasticity<sup>15-17</sup>, from which the modulus is given by

$$[f^*] = [f_{ph}^*] (1 + f_c/f_{ph}) \quad (4)$$

where  $[f_{ph}^*]$  is the modulus for the corresponding phantom network and  $f_c$  and  $f_{ph}$  are the contributions to the force from the constraints on fluctuations of junctions and from the equivalent phantom network respectively. The ratio  $f_c/f_{ph}$  is given by the theory as a function of two parameters,  $\kappa$ , which is a measure of the severity of the constraints, and  $\zeta$ , which is related to the degree of non-affineness in the relaxation of those constraints with strain<sup>17</sup>.

The most important parameter,  $\kappa$ , has been reported to be a function of the degree of crosslinking<sup>18-20</sup> as expressed by the phantom modulus  $[f_{ph}^*]$ , the dimensions of the polymer chains and the functionality in such a way that for PAA networks the following relationship is found<sup>12</sup>

$$\kappa = 3.32 [f_{ph}^*]^{-1/2} \quad (5)$$

Therefore the data were fitted by adjusting simultaneously  $\kappa$  and  $[f_{ph}^*]$  along with the value of  $\zeta$ . The stress-strain isotherms have been reported elsewhere<sup>12</sup>. The most important features that can be drawn from those results are the following:

- i) For the lowest values of  $C$  (set of gels with

constant  $C_T$ ) and the lowest values of  $C_T$  (set of gels with constant  $C$ ), the modulus is almost invariant when it is represented as a function of  $\alpha^{-1}$ , as expected for very dilute networks ( $C_2 \approx 0$  in the Mooney-Rivlin equation)

ii) When the crosslinker ratio or the total concentration are raised, deviations from the linearity or upturns, are observed; in both cases this is accompanied with a decrease in the rupture elongation. These observations may be attributed to non-gaussian effects (not accounted for in the theory of Flory) due to the increasing heterogeneity of the gels.

A detailed analysis of the type and proportion of network defects, that are ultimately responsible of the above mentioned heterogeneity, is required in order to interpret properly the elastic measurements.

TABLE I

Characteristics and elastic results on PAA gels obtained at constant crosslinker proportion  $C=10\%(w/w)$

Gel	$C_T$ (g/100ml)	$v_{2c}$	$[f^*_{ph}]$ (N.mm <sup>-2</sup> )	$\alpha_r$	$\frac{M^{\text{exp}}_c}{M^{\text{th}}_c}$	$v^{\circ}_{2s}$
T-1	18.0	0.145	0.311	1.10	2.13	0.158
			0.336	1.10	2.03	0.156
T-2	15.0	0.119	0.119	1.27	3.97	0.128
			0.150	1.28	5.19	0.126
T-3	11.0	0.0872	0.0685	1.30	6.91	0.0903
			0.0723	1.27	6.36	0.0862
T-4	7.67	0.0600	0.0217	1.35	18.5	0.0587
			0.0265	1.48	14.8	0.0627
T-5	6.72	0.0525	0.0193	1.54	18.6	0.0487
			0.0170	1.64	21.6	0.0484
T-6	4.99	0.0388	0.0074	1.73	41.6	0.0388
			0.0072	1.53	42.3	0.0381

From the point of view of the mechanism of gelation it can be easily understood that increasing dilution of the initial monomers mixture (low  $C_T$  values), departures from the chemical crosslinking degree (calculated from the initial proportion of BA) are going to be large, that is to say, a larger proportion of defects and elastically non-effective structures are going

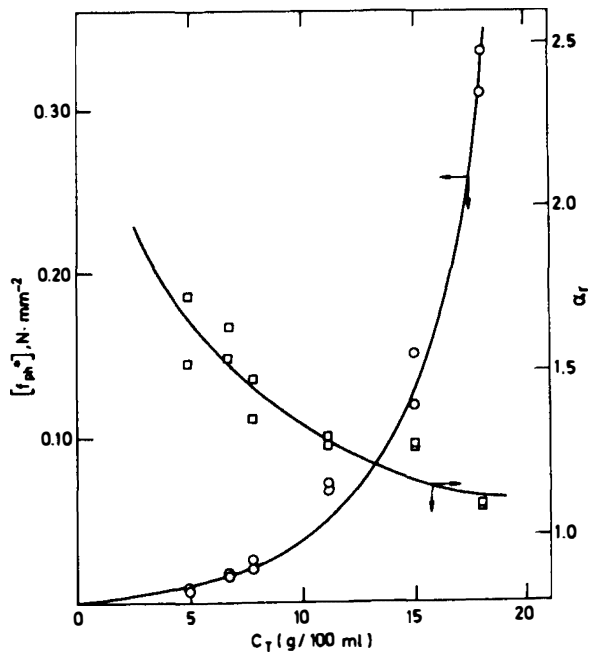


Fig.1.- Phantom modulus  $[f^*_{ph}]$ , ( $\circ$ ), and rupture elongation  $\alpha_r$ , ( $\square$ ), plotted as a function of the total monomer concentration  $C_T$  (g/100 ml), at fixed crosslinker weight fraction

to be found<sup>21</sup>. As a consequence the effective crosslinking degree is going to be reduced, varying also the magnitudes related with it; this is reflected in the lower values of the polymer volume fractions,  $v^{\circ}_{2S}$ , (Table I) and the lower values of the elastic modulus (Fig.1). The habit of the variation of  $\alpha_r$  agrees well (Fig.1) with what it has just been mentioned above; the rupture elongation increases as  $[f^*_{ph}]$  decreases, indicating that larger PAA chains between knots are formed.

Since increasing total concentration ( $C_T$ ) has the effect of shortening the chains, a gradual change from gaussian to non-gaussian behavior results. This is really observed in the stress-strain isotherms<sup>12</sup>.

Another effect, even more important, to explain the up-

turns, that occur simultaneously, is the presence of a large proportion of highly crosslinked regions or clusters that would act as reinforcements<sup>22</sup>. The mechanism from which these clusters are formed will be discussed below.

TABLE II

Characteristics and elastic results on PAA gels obtained at constant total concentration  $C_T = 6.72$  g/100 ml

Gel	C (% w/w)	$v_{2c}$	$[f^*_{ph}]$ (N.mm <sup>-2</sup> )	$\alpha_r$	$\frac{M_c^{exp}}{M_c^{th}}$	$v^o_{2s}$
C-1	0.663	0.0515	0.0026	2.43	7.7	0.0124
			0.0022	2.60	9.9	0.0138
C-2	1.134	0.0515	0.0093	2.21	3.6	0.0293
C-3	2.599	0.0523	0.0130	1.78	6.7	0.0303
			0.0138	1.72	6.7	0.0314
C-4	3.950	0.0522	0.0192	1.72	6.7	0.0403
C-5	5.784	0.0524	0.0165	1.55	12.2	0.0463
			0.0192	1.60	10.3	0.0443
C-6	6.951	0.0521	0.0195	1.43	12.3	0.0501
			0.0190	1.62	12.6	0.0571
C-7	8.756	0.0522	0.0154	1.38	20.1	0.0463
C-8	11.91	0.0523	0.0135	1.44	32.3	0.0475
			0.0135	1.58	32.3	0.0498
C-9	13.98	0.0531	0.0100	1.40	52.2	0.0460
			0.0108	1.44	49.4	--
C-10	14.50	0.0521	0.0103	1.31	53.6	0.0487

With regard to the absolute values of the modulus and its variation with C, keeping constant  $C_T$  (Table II), this behavior is more complicated as shown in Fig.2. Increasing BA monomer percentage, first causes an increase in modulus but after  $C = 5-6\%$ (w/w), the modulus levels off and then decreases. Therefore there is a range of values of C in which the mechanical properties are enhanced, since the modulus has a maximum, without losing ultimate properties ( $\alpha_r$  almost remains constant). Increasing further the percentage of crosslinking monomer does not improve the elastic properties of the gels.

At low values of C a linear relationship between shear modulus and BA proportion<sup>23-24</sup> has been reported. However some other studies<sup>7,8</sup> have shown a similar behavior as the one reported here when a broader range of crosslinker concentrations is considered. It should be noticed that the departure from



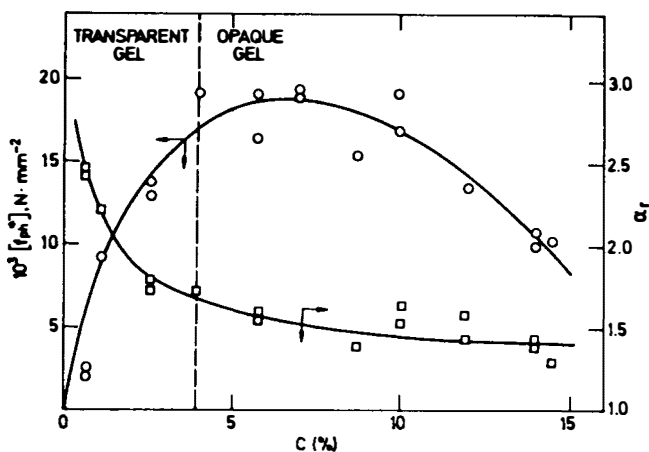


Fig.2.- Phantom modulus  $[f^*_{ph}]$ , (○) and rupture elongation  $\alpha$ , (□), plotted as a function of crosslinker weight fraction  $C(\%)$ , at fixed  $C_T$

linearity coincides with the transparent gel-opaque gel boundary on the phase diagram reported by Bansil and Gupta<sup>25</sup>. On the other hand, the modulus has been reported to increase exponentially with  $C_T$  in the transparent gel zone of the phase diagram<sup>7</sup>. The same behavior has been observed here (Fig.1) from samples corresponding to the opaque-gel region.

All these features should be related to the molecular structure of the gels. It is well known that PAA gels are very heterogeneous and a number of different models for their structure have been proposed<sup>1-10</sup>. All these models consider two different regions in the gel: a number of highly cross-linked aggregates or clusters linked together by a more lightly crosslinked gel, thus resulting in a two-phase structure.

In previous studies on the kinetics of the gelation process<sup>9,10</sup>, we have reported the different reactivity ratios of both comonomers, AA and BA, being  $r_{AA}=0.57$  and  $r_{BA}=3.4$ . These values are given as monomer reactivity coefficients and not as vinyl reactivity coefficients, and the higher value for BA is reasonable since BA has two vinyl groups; this is the reason

why the crosslinker seems to enhance the polymerization kinetics as observed in other systems<sup>26</sup>. Therefore there are two important consequences that must be taken into account: the composition of the feeding mixture changes with conversion and the primary chains are richer in BA than the feeding mixture. These effects are dependent on the mole fraction of BA; when the BA proportion is very small, the differences in the composition of the primary chains, assuming equal or different values for  $r_{AA}$  and  $r_{BA}$ , have presumably little influence on the macroscopic properties of the final gel. When the amount of crosslinker is appreciable, there is a conversion dependent shift on the chemical composition of the gel that may contribute to the total heterogeneity of the system.

At the same time, since BA has larger tendency than AA to be incorporated into the gel, the crosslinker forms sequences whose length and probability of appearance may be easily calculated with the assumption of first order Markovian statistics<sup>10,27</sup>. This assumption is justified since any penultimate-unit (or higher order) effect that may be considered, would affect essentially the absolute values of the propagation rate constant and not the composition distribution<sup>28</sup>. Moreover, since AA has a very high  $k_p/k_t^{1/2}$  value, chains with very high polymerization degrees are formed.

Each sequence of length  $n$  may behave as a multifunctional knot with a functionality given<sup>10</sup> by  $2n+2$ . Obviously, the existence of BA sequences will reduce the crosslinking ability of the crosslinker in comparison with the situation in which the crosslinker is uniformly distributed along the chains. It can easily be shown<sup>27</sup> that for a network with  $C=5\%$ (w/w), the average functionality per knot increases about 9%, but the number of chains, that may be crosslinked, decreases for about 7.5% with respect to the maximum crosslinking ability (in the most favourable case in which all the vinyl groups of the BA sequence are "active").

The elastic modulus is a function of both, the average functionality and the number of knots. Since increasing functionality is accompanied with a simultaneous decrease of the number of knots, both effects may compensate each other and only an upturn at relatively small elongations would be observed due to the filler effect of the multifunctional knots.

With regard to the form of the stress-strain isotherms, the variation with  $C$  of the length of the elastic parts of the chains has even a more decisive influence. As an approximation we can consider a sequence of AA between two BA units (or sequences) as an elastic chain. The number of chain bonds below which the chain may not be described by gaussian statistics<sup>14</sup> can be taken as 100; therefore, sequences of AA with a length shorter than 50 monomer units may be considered as non gaussian chains. For a chain of infinite length it can easily be shown that the percentage of AA sequences with lengths shorter than 50, is given by<sup>27</sup>

$$\sum_{n=1}^{50} W_n^{AA} = (1 - W_1^{AA}) \sum_{n=1}^{50} (W_1^{AA})^{n-1} = 1 - (W_1^{AA})^{50} \quad (6)$$

where  $W_n^{AA}$  is the probability that a closed sequence of AA has a length  $n$ , and  $W_1^{AA}$  is the same probability for a sequence of length 1. For values of  $C$  starting from 3-4% (w/w), simple calculations can demonstrate that more than 80% of AA sequences behave as non-gaussian chains. This is in very good accordance with elastic measurements on bimodal poly(dimethylsiloxane) networks<sup>22</sup> which show that a large proportion of shorter chains is necessary to observe upturns of the modulus.

So far we have discussed the direct dependence of the chemical distribution on the elastic behavior of PAA gels. But there is another important group of network imperfections, responsible of the observed maximum in the modulus, that are related also with the composition distribution but via the gelation mechanism. Previous studies on the gelation of PAA networks<sup>11</sup> have reported the existence of a minimum in the dependence of the gel conversion on  $C$ , at the same value at which a maximum of the modulus is observed. The minimum of the gel point was explained in terms of a balance between crosslinking and cyclization reactions, both processes involving a pendant vinyl group. When  $C$  takes a value around 5-7% (w/w) the sequence length of AA is about 10, that is to say, 20 skeletal bonds. On average, every 10 AA units, the AA sequence is ended by a sequence of BA. On the other hand, the cyclization probability is a function, among other factors, of the cycle length, being maximum for a length of 20 for very flexible polymer chains<sup>21</sup>. Therefore, cyclic formation begins

to be important at this stage. At higher values of C, intra-molecular reactions rather than crosslinking seem to prevail, resulting in a large proportion of cycles.

It is particularly interesting to note the coincidence between the properties of the gels just in the gel point and at final conversion. This suggests that post-gel reactions do not differ too much of the pre-gel reactions when very dilute systems like the one presented here are involved.

The existence of inelastic structures or imperfections on PAA gels can be evaluated by comparison of the degree of crosslinking that can be calculated by the phantom moduli, with the theoretical value obtained if the crosslinking process were ideal and the whole gel structure were elastic. From the phantom modulus, the effective molecular weight between crosslinks,  $M_c^{exp}$ , can be calculated by means of the equation<sup>29</sup>

$$M_c^{exp} = (1 - 2/\phi) (dRT / [f_{ph}^*]) (v_{2c})^{2/3} \quad (7)$$

where  $\phi$  is the functionality;  $d$  the density;  $v_{2c}$  the volume fraction of the gel at the moment of the gel formation, and other symbols have their usual meaning.

The theoretical molecular weight,  $M_c^{th}$ , can be calculated by the equation<sup>12</sup>

$$M_c^{th} = [AA] M_{AA} / (2 [BA]) \quad (8)$$

where  $[AA]$  and  $[BA]$  are the mole concentrations of AA and BA, and  $M_{AA}$  is the molecular weight of AA.

The comparison has been made as the ratio between experimental and theoretical values of  $M_c$ , and is presented in the fifth column of Tables I and II and in Fig.3.

As can be seen from this figure, departures from ideality (higher values of the ratio  $M_c^{exp}/M_c^{th}$ ) are more pronounced when dilution or crosslinker proportion increase. In both cases, the crosslinking effectiveness is decreased, but in the set of gels synthesized at constant C, an asymptotic trend is suggested; this is consistent with the existence of a critical value of the total concentration below which only a sol phase would be formed with an infinite value for  $M_c^{exp}$ . This critical

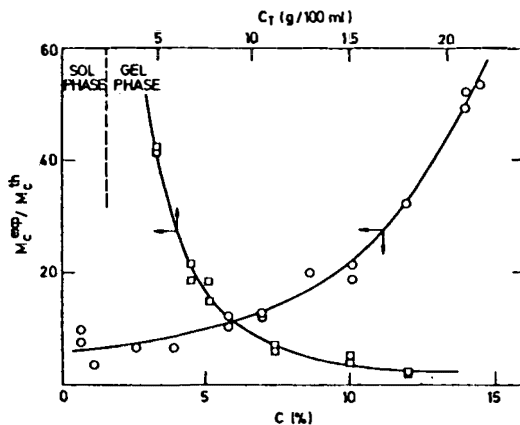


Fig.3.- The ratio  $M_c^{\text{exp}}/M_c^{\text{th}}$  plotted as a function of  $C_T$ , ( $\square$ ), at constant  $C$ , and as a function of  $C$ , ( $\circ$ ), at constant  $C_T$ .

value has been reported by experimental<sup>25</sup> and theoretical studies<sup>30</sup>

When  $C_T$  is increased, or  $C$  decreased, more perfect gels are formed. In both cases the value of 1 for the ratio  $M_c^{\text{exp}}/M_c^{\text{th}}$  is suggested to be reached because of the greater effectiveness of the crosslinking process. In the former case (high  $C_T$ ) short chains and high moduli are going to be obtained; whereas in the later case (low  $C$ ) the crosslinker is going to be more uniformly distributed and low cycles content is going to be obtained.

#### ACKNOWLEDGEMENTS

This work was supported by a grant from the CAICYT (0528/84). The authors wish to thank Dr. A. Horta and Dr. J. Freire for many helpful discussions.

## REFERENCES

- 1.- T.P. Hsu and C. Cohen, Polymer **25**, 1419 (1984)
- 2.- M.K. Gupta and R. Bansil, J. Polym. Sci., Polym Lett Ed. **21**, 969 (1983)
- 3.- E.G. Richard and C.J. Temple, Nature (Phys. Sci.) **22**, 92 (1971)
- 4.- E. Geissler, A.M. Hecht and R. Duplessix, J. Polym. Sci. A-2 **20**, 225 (1982)
- 5.- N. Weiss, Polymer Science and Technology, Vol 16, A.R. Cooper Ed., Plenum Press, N.Y. 1981
- 6.- N. Weiss, T.T. Van Vliet and A. Silberberg, J. Polym. Sci., Polym. Phys. Ed. **19**, 1505 (1981); ibid, **17**, 2229 (1979)
- 7.- N. Weiss and A. Silberberg, Br. Polym. J., **9**, 144 (1977)
- 8.- T.P. Hsu, D.S. Ma and C. Cohen, Polymer, **24**, 1273 (1983)
- 9.- J.L. Nieto, J. Baselga, I. Hernandez-Fuentes, M.A. Llorente and I.F. Piérola, Eur. Polym. J., **23**, 551 (1987)
- 10.- J. Baselga, M.A. Llorente, J.L. Nieto, I. Hernandez-Fuentes and I.F. Piérola, Eur. Polym J., **24**(2), 161 (1988).
- 11.- J. Baselga, M.A. Llorente, I. Hernandez-Fuentes and I.F. Piérola, in preparation
- 12.- J. Baselga, I. Hernandez-Fuentes, I.F. Piérola and M.A. Llorente, Macromolecules, **20**, 3060 (1987)
- 13.- J.E. Mark and J.L. Sullivan, J. Chem. Phys., **66**, 1006 (1977)
- 14.- P.J. Flory, "Principles of Polymer Chemistry", Ithaca, N.Y. 1953. Chap. 13.
- 15.- P.J. Flory, Br. Polym. J., **17**, 96 (1985)
- 16.- P.J. Flory, J. Chem. Phys., **66**, 5720 (1977)
- 17.- P.J. Flory and B. Erman, Macromolecules, **15**, 800 (1982)
- 18.- B. Erman and P.J. Flory, Macromolecules, **15**, 808 (1982)
- 19.- R.N. Brozman and J.E. Mark, Macromolecules, **19**, 667 (1986)
- 20.- J. San Juan and M.A. Llorente, J. Polym. Sci., Part B, Polym. Phys. **26**, 235 (1988)
- 21.- K. Dusek and M. Ilavsky, J. Polym. Sci., Symp., **53**, 75 (1975)
- 22.- M.A. Llorente, A.L. Andrady and J.E. Mark, J. Polym. Sci., Polym. Phys. Ed., **19**, 621 (1981)
- 23.- R. Nossal, Macromolecules, **18**, 49 (1985)
- 24.- W. Oppermann, S. Rose and G. Rehage, Br. Polym. J. **17**, 175 (1985)
- 25.- R. Bansil and M.K. Gupta, Ferroelectrics, **30**, 62 (1980)

- 26.- J.P. Munch, M. Aubrim, G. Hild, R. Okasha and S. Candau, Macromolecules, 17, 110 (1984)
- 27.- J.Baselga, Ph. D. Thesis. Universidad Complutense, Madrid (1987)
- 28.- T.Fukuda, Y-D.Ma, H.Inagaki,Makromol.Chem.,Rapid Commun., 8, 495 (1987)
- 29.- A.L.Andrady and M.A. Llorente, J.Polym.Sci.,Part B,Polym. Phys.Ed., 25, 195 (1987)
- 30.- R.Bansil, H.J.Herrmann and D.Stauffer,Macromolecules, 17, 998 (1984)